

GRANEL

mai/2024


Dia	Composição Química				Resistência a Compressão			Finura				Expansibilidade	Pega		Consist.
	P. Fogo (%)	RI (%)	SO3 (%)	CaO Livre (%)	03 Dias MPa	07 Dias MPa	28 Dias Mpa	Massa Espec. (g/cm ³)	Blaine (m ² /Kg)	# 325 (%)	# 200 (%)	Quente (mm)	Início (min)	Fim (min)	Normal (%)
1	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---
2	2,36	0,36	1,62	0,74	22,8	33,5	---	3,01	5345	0,8	0,2	0,0	178	190	30,4
3	1,99	0,27	1,58	0,71	22,0	33,2	---	3,00	5135	0,8	0,2	0,0	170	185	30,4
4	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---
5	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---
6	1,73	0,28	1,73	0,82	24,4	33,1	---	3,01	5367	0,8	0,2	0,0	175	213	30,2
7	1,59	0,31	1,69	0,84	22,6	32,8	---	3,01	5111	0,8	0,2	0,0	178	228	30,4
8	1,65	0,33	1,66	0,69	23,9	32,0	---	3,01	5299	0,8	0,2	0,0	165	218	30,1
9	1,77	0,38	1,80	0,73	24,2	33,1	---	3,01	5253	0,8	0,2	0,0	162	222	30,1
10	1,83	0,42	1,65	0,74	23,2	33,0	---	3,01	5458	0,8	0,2	0,0	170	225	30,2
11	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---
12	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---
13	1,83	0,33	1,72	0,76	20,4	31,1	---	3,00	5253	0,8	0,2	0,0	160	218	30,1
14	1,86	0,32	1,76	0,79	20,7	---	---	3,00	5299	0,8	0,2	0,0	153	215	30,1
15	---	---	---	---	20,2	---	---	3,00	5182	0,8	0,2	0,0	180	265	30,2
16	1,85	0,46	1,65	0,81	---	---	---	3,00	5087	0,8	0,2	0,0	178	260	30,2
17	---	---	---	---	---	---	---	3,00	5276	0,8	0,2	0,0	182	268	30,2
18	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---
19	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---
20	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---
21	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---
22	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---
23	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---
24	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---
25	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---
26	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---
27	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---
28	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---
29	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---
30	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---
31	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---

Controle Estatístico

	R3	R7	R28												
MÉDIA	1,85	0,35	1,69	0,76	22,4	32,7	#DIV/0!	3,01	5255	0,8	0,2	0,00	171	226	30,2
DESVIO	0,21	0,06	0,07	0,05	1,57	0,79	#DIV/0!	0,01	110,73	0,00	0,00	0,00	9,19	26,72	0,12
ABNT	≤6,5	≤ 5,0	≤ 4,5		≥ 12,0	≥ 23,0	≥ 40,0					≤ 8,0	≤ 5	≥ 60	≤ 720

(*) Amostra reanalisada

COMPARATIVO ABNT X MIZU

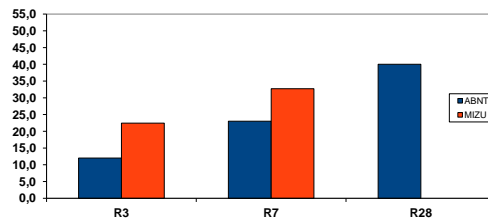

[Assinatura]

Líder de Fábrica
Rogério Americano Alves

[Assinatura]

Responsável Técnica
Jessika Mouta Guimarães
CRQ.03426796 - 3ª Região